


# 100-70-03 Ductile Iron

## General Description:

Dura-Bar 100-70-03 ductile iron contains nodular graphite in a matrix of pearlite with small amounts of ferrite. The pearlitic structure maximizes strength and wear characteristics in a non-alloyed as-cast ductile iron. This specification is similar to ASTM A536 100-70-03.

## Microstructure:

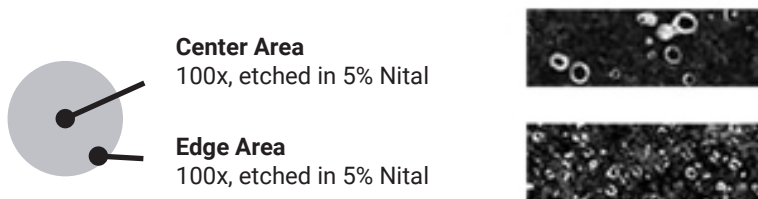

The microstructure consists of Type I & Type II nodular graphite as defined in ASTM A247. The matrix is highly pearlite with small amounts of ferrite. The edge or rim will have a higher nodule count and contain slightly higher ferrite concentration when compared to the center. Chill carbides will be less than 5% in any field at 100x and will be well dispersed.

## Heat Treat Response:

Dura-Bar 100-70-03 can be oil quench hardened from 1600° F (885° C) to a minimum hardness of Rockwell C 50 on the outside of the bar. The inside diameter hardness will be less than Rockwell C 50. Lower quench hardness on the inside diameters are a result of larger graphite nodules and not a loss of matrix hardness. Get more details including typical Jominy end quench curve, methods and cycle times, and temperature effects by downloading the Dura-Bar Heat Treating Guide.

## Chemical Composition:

Element	Percentage
Carbon*	3.50 - 3.90%
Silicon*	2.25 - 3.00%
Manganese	0.15 - 0.35%
Sulfur	0.025% Max
Phosphorus	0.05% Max

\*Carbon and silicon targets are specified for each bar size in order to maintain mechanical properties. Small amounts of alloying elements are used to stabilize the pearlitic structure. Magnesium treatment is employed to produce nodular graphite.

## Mechanical Properties:

Hardness properties for various diameters are shown in the table. Hardness properties listed are minimum and maximum across the bar. For rectangles, squares and shapes, the hardness properties will depend on minimum and maximum section thickness and will be supplied on request.

Size Range		BHN	
Inches	mm	Min	Max
1.000 – 20.000	25 – 508	255	302

Tensile strength is determined from a longitudinal test specimen taken from mid-radius of the as-cast bar.

Mechanical Properties	
Tensile strength psi (min)	100,000
Yield strength psi (min)	70,000
Elongation (min)	3%

## Typical Applications:

### Automotive:

Gears

### Fluid Power:

Cylinder blocks, End Caps, Gear Rack Housings, Gerotors, Glands, Manifolds, Pistons, Rotors, Valves

### Glass Mold:

Bank Molds, Plungers

### Machinery:

Barrell Rollers, Bushings, Chain Sheave Rollers, Chuck Bodies, Die Blocks, Flywheels, Gear Racks, Gears, Housings, Pile Drivers, Press Rams, Pulleys, Rams, Rotary Tables

### Miscellaneous:

Port Plate

### Power Transmission:

Gears, Pulleys

### Pump and Compressor:

Gears, Housings, Pistons, Rotors

### Steel Mill:

Guide Rolls, Pinch Rolls, Runout Table Rolls

### Transportation:

Camshafts, Carriers, Gears, Pulleys, Rail Spacers

Visit [www.petersonsteel.com](http://www.petersonsteel.com) to see successful applications being made from Dura-Bar, including their design and cost benefits.

Contact us today to discuss your application and how you can start saving with Dura-Bar..